

Original citation:

Michor, H., Sereni, J. G., Giovannini, M., Kampert, Erik, Salamakha, L., Hilscher, G. and Bauer, E.. (2017) Elucidating the lack of magnetic order in the heavy-fermion CeCu₂Mg. Physical Review B, 95 (11). 115146.

Permanent WRAP URL:

<http://wrap.warwick.ac.uk/87959>

Copyright and reuse:

The Warwick Research Archive Portal (WRAP) makes this work by researchers of the University of Warwick available open access under the following conditions. Copyright © and all moral rights to the version of the paper presented here belong to the individual author(s) and/or other copyright owners. To the extent reasonable and practicable the material made available in WRAP has been checked for eligibility before being made available.

Copies of full items can be used for personal research or study, educational, or not-for-profit purposes without prior permission or charge. Provided that the authors, title and full bibliographic details are credited, a hyperlink and/or URL is given for the original metadata page and the content is not changed in any way.

Publisher statement:

© 2017 American Physical Society

A note on versions:

The version presented here may differ from the published version or, version of record, if you wish to cite this item you are advised to consult the publisher's version. Please see the 'permanent WRAP URL' above for details on accessing the published version and note that access may require a subscription.

For more information, please contact the WRAP Team at: wrap@warwick.ac.uk

Elucidating the lack of magnetic order in the heavy fermion CeCu₂Mg

H. Michor¹, J.G. Sereni², M. Giovannini³, E. Kampert⁴, L. Salamakha¹, G. Hilscher^{1†}, E. Bauer¹

¹*Institute of Solid State Physics, TU Wien, A-1040 Wien, Austria*

²*Low Temperature Division CAB-CNEA, CONICET, 8400 S.C. de Bariloche, Argentina*

³*Dipartimento di Chimica e Chimica Industriale, Università di Genova, I-16146 Genova, Italy
and CNR-SPIN Corso Perrone, I-16152 Genova, Italy*

⁴*Dresden High Magnetic Field Laboratory, Helmholtz-Zentrum Dresden-Rossendorf, D-01314 Dresden, Germany*

(Dated: December 6, 2016)

Magnetic, transport, and thermal properties of CeCu₂Mg are investigated to elucidate the lack of magnetic order in this heavy fermion compound with a specific heat value, $C_{\text{mag}}/T|_{T \rightarrow 0} \approx 1.2 \text{ J/mol K}^2$ and robust effective magnetic moments ($\mu_{\text{eff}} \approx 2.46 \mu_B$). The lack of magnetic order is attributed to magnetic frustration favored by the hexagonal configuration of the Ce sub-lattice. In fact, the effect of magnetic field on C_{mag}/T and residual resistivity ρ_0 does not correspond to that of a Fermi-liquid (FL) because a broad anomaly appears at $T_{\text{max}} \approx 1.2 \text{ K}$ in $C_{\text{mag}}(T)/T$, without changing its position up to $\mu_0 H = 7.5 \text{ T}$. However, the flattening of $C_{\text{mag}}/T|_{T \rightarrow 0}$ and its magnetic susceptibility $\chi_{T \rightarrow 0}$, together with the T^2 dependence of $\rho(T)$, reveal a FL behavior for $T \leq 2 \text{ K}$ which is also supported by Wilson and Kadowaki-Woods ratios. The unusual coexistence of FL and frustration phenomena can be understood by placing this compound at the so-called 'strange metal' region of a frustration-Kondo model. The entropy, S_{mag} , reaches $0.87 R \ln 6$ at $T \simeq 100 \text{ K}$, with a tendency to approach the expected value $S_{\text{mag}} = R \ln 6$ of the $J = 5/2$ ground state of Ce^{3+} .

I. INTRODUCTION

Heavy fermions are characterized by a high density of low energy excitations that increases by lowering the temperature. This scenario is induced by the hybridization (Γ_{sf}) of the localized $4f$ and conduction states [1], producing a progressive screening of the $4f$ magnetic moments as the temperature drops below a characteristic (Kondo) temperature, $T_K \propto \Gamma_{sf}$. For large T_K values (strong hybridization) magnetism is suppressed because magnetic moments are fully screened by conduction electron spins and the system behaves as a Fermi liquid (FL), where the Sommerfeld coefficient of the specific heat $\gamma = C_{\text{mag}}/T \propto m_{\text{eff}}$, with C_{mag} being the magnetic contribution to specific heat and m_{eff} the effective mass of FL quasi-particles. For intermediate T_K (moderate Γ_{sf}), the ground state (GS) degrees of freedom progressively accumulate at low energy, with a consequent growing of the density of states reflected in the γ enhancement.

Upon a further decrease of T_K , $C_{\text{mag}}/T \equiv \gamma_T$ becomes temperature dependent at $T \rightarrow 0$. In this non-Fermi liquid regime, a typical $C_{\text{mag}}(T)/T \propto -\ln(T/T_0)$ dependence is observed [2], where T_0 represents an energy scale similar to T_K for FL systems. Depending on the number of electrons in the conduction band, the electronic spins may or not be able to fully screen the localized magnetic moments. In the so called under-screened regime [3], the system may order magnetically (at T_{ord}), with a fraction of the total GS degrees of freedom (usually $R \ln 2$) condensed into the ordered phase when $T_{\text{ord}} \approx T_K$.

In the Doniach-Lavagna [4, 5] model, the competition between T_{ord} and T_K depends on the ratio of the respective coupling parameters J_{ord} and J_K . For low values, the system is expected to order magnetically because $T_{\text{ord}} \propto J_{\text{ord}}^2$ grows faster than $T_K \propto \exp[-1/n(E_F)J_K]$ where $n(E_F)$ is the electronic density of states at the

Fermi level. There is, however, an increasing number of Ce and Yb based compounds that do not order magnetically despite of their robust magnetic moments, i.e. possessing low T_K values [6]. This is the case of ternary CeCu₂Mg crystallizing in the GdPt₂Sn type structure [7].

Different origins can be argued for such anomalous behavior: i) dilute or disordered magnetic moments, ii) large interatomic distance between magnetic atoms, iii) weak exchange interaction J_{ord} or iv) frustrated magnetic interactions. Alternative i) does not apply to a Ce-lattice compound neither ii) because in CeCu₂Mg the Ce-Ce distance lies within the range of many ordered compounds [8].

With the aim to verify the lack of magnetic order below $T = 1.5 \text{ K}$ and to elucidate the nature of the GS of this compound, magnetic and thermal properties are newly studied in this work extending the range of measurements down to $T \approx 0.5 \text{ K}$.

II. EXPERIMENTAL DETAILS

The samples were prepared using cerium 99.9 mass %, magnesium and copper 99.99 mass % supplied by Newmet Koch, Waltham Abbey, England as starting materials. The samples were prepared by induction melting stoichiometric amounts of the elements enclosed in a small arc-sealed tantalum crucibles. The alloys were then annealed at 500°C for 20 days and characterized by electron probe micro-analysis (EPMA) and X-ray powder diffraction (XRD).

Magnetization was measured employing a CRYOGENIC S700X superconducting quantum interference device (SQUID) magnetometer at temperatures from 0.3 to 2 K with a ^3He -insert and from 1.8 K to room temperature with standard ^4He variable temperature insert.

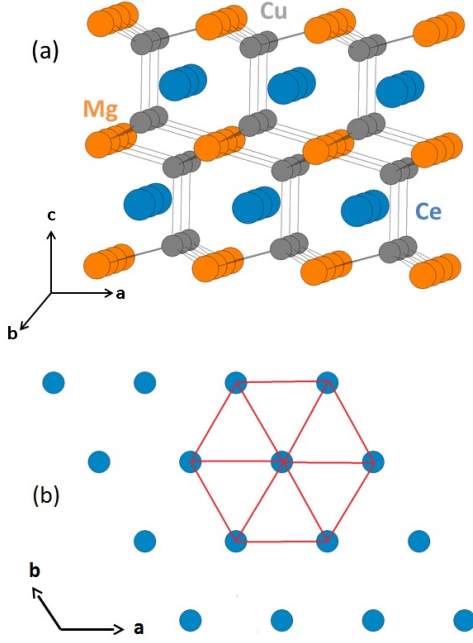


FIG. 1. (Color online) (a) Crystal structure of CeCu₂Mg. Cerium (blue), copper (gray) magnesium (orange). (b) Ce-layers in the 'ab' plane. The hexagonal lattice of Ce atoms is sketched for a Ce atom having six first neighbors.

An additional high-field magnetization measurement at 1.6 K and at fields up to 60 T was performed at the Dresden High Magnetic Field Laboratory using a pulse field system with a 1.44 MJ capacitor module (see Ref. [9] for further details).

Low temperature specific heat data were measured using various setups: (i) with a standard heat pulse technique in a semi-adiabatic He-3 calorimeter in the range between 0.5 and 7 K, at zero and applied magnetic field up to 4 T, (ii) with a Quantum Design PPMS relaxation-type calorimeter with ³He-insert between 0.5 and 10 K in magnetic fields up to 7.5 T, (iii) with PPMS ⁴He specific heat buck in zero-field and a temperature range of 2 to 120 K.

The electrical resistivity and magneto-resistivity of bar shaped samples (about $0.5 \times 0.5 \times 3 \text{ mm}^3$) were measured using a four-probe ac bridge method with spot-welded gold contacts in the temperature range from 0.4 K to 25 K and in magnetic fields up to 12 T.

III. EXPERIMENTAL RESULTS

A. Structural properties

A refinement of X-ray patterns for CeCu₂Mg [7] confirmed that this compound crystallizes in the hexagonal

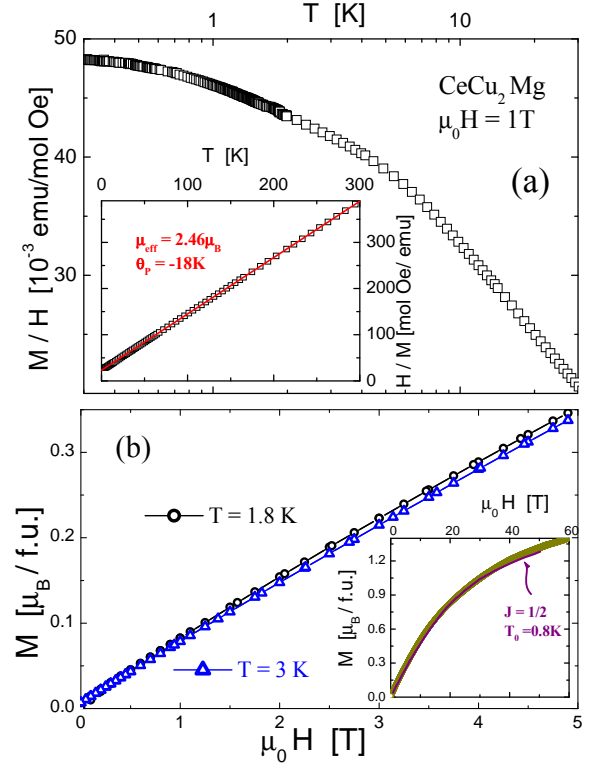


FIG. 2. (Color online) (a) Low temperature ($T < 25 \text{ K}$) thermal dependence of the magnetic susceptibility in a semi-logarithmic representation. Inset: Temperature dependent inverse magnetic susceptibility, with a Curie-Weiss fit, Eqn. (1), shown as solid line. (b) Field dependent isothermal magnetization at temperatures as labeled. Inset: High field magnetization data measured up to 60 T at 1.6 K.

GdPt₂Sn structure type (space group $P6_3/mmc$), named also as ZrPt₂Al- or LiCu₂Sn- type [10]. The lattice parameters are $a = 4.657 \text{ \AA}$ and $c = 8.654 \text{ \AA}$. In this hexagonal structure constituent atoms are stacked in layers perpendicular to the c axis in regular sequences of Mg, Cu, Ce, and Cu as shown in Fig. 1a. In the Ce-layers atoms are well separated from each other, forming a hexagonal lattice (shown in Fig. 1b) where Ce atoms have six first neighbors placed at the Ce-Ce shortest distances corresponding to the lattice parameter a . Moreover, Ce atoms fill large highly symmetric rhombic dodecahedron cages of coordination number 14 (8 Cu + 6 Mg).

B. Magnetic Properties

The low temperature ($T < 25 \text{ K}$) thermal dependence of the magnetic susceptibility (defined as $\chi = M/H$) is shown in Fig. 2a in a semi-logarithmic representation. Below about 10 K $\chi(T)$ tends to flatten due to an antiferromagnetic interaction, which leads to a negative paramagnetic Curie temperature $\theta_p = -18 \text{ K}$ [7]. Above 10 K,

the usual $\chi \propto 1/T$ dependence is recovered (see the inset of Fig. 2a). The experimental results are properly described by a classical Curie-Weiss law, including a moderate Pauli like contribution (χ_0):

$$\chi = C/(T + \theta_p) + \chi_0, \quad (1)$$

with the Curie constant $C = N_A \mu_{\text{eff}}^2 / 3k_B$. μ_{eff} is the effective paramagnetic moment. The values derived are: $\mu_{\text{eff}} = 2.46 \mu_B$, $\theta_p = -18 \text{ K}$ and $\chi_0 = 3.5 \times 10^{-3} \text{ emu/mol Oe}$. These values confirm the robustness of the Ce^{3+} moments and are consistent with those reported in Ref. [7] with the same θ_p and a $\mu_{\text{eff}} = 2.53 \mu_B$. In the inset of Fig. 2a the high temperature range is depicted as the inverse susceptibility after subtracting χ_0 .

The field dependence of the magnetization, measured up to $\mu_0 H = 5 \text{ T}$, is displayed in Fig. 2b. Only a slight variation in the slope of $M(H)$ is observed between 1.8 and 3 K, in agreement with the flattening of the $\chi(T)$ dependence at low temperature. Further magnetization measurements at $T = 1.5 \text{ K}$ extended up to $\mu_0 H = 60 \text{ T}$ (see inset of Fig. 2b) reveal a continuous increase of $M(H)$ with a progressive curvature approximately described by the Coqblin-Schrieffer model [11] with $J = 1/2$ and $T_0 = 0.8 \text{ K}$ as a characteristic Kondo energy scale.

C. Electrical Resistivity

Zero-field electrical resistivity data of CeCu_2Mg and LaCu_2Mg were earlier reported for the temperature range 4–300 K revealing a tilde shape temperature dependence (in $\rho(T)$ vs $\log T$) for CeCu_2Mg , with a local maximum at about 8.5 K and a local minimum at about 80 K, and a normal metallic behavior for LaCu_2Mg [7]. In the present study, temperature and field dependent resistivity measurements, $\rho(T, H)$, were extended down to 0.5 K and up to 12 T. A slightly positive curvature at lowest temperatures reveals a Fermi liquid-like behavior, $\rho(T, H) \simeq \rho_0(H) + A(H)T^2$, below about 2 K (see Fig. 3a). The most remarkable features are a substantial reduction of the residual resistivity $\rho_0(H)$ by about 30% when increasing the magnetic field from zero to 8 T, $\rho_0(0 \text{ T}) = 27.3 \mu\Omega\text{cm}$ and $\rho_0(8 \text{ T}) = 21.1 \mu\Omega\text{cm}$, and a non-monotonous but weak variation of the T^2 -coefficient $A(H)$ which is $0.85 \mu\Omega\text{cm K}^{-2}$ at zero field, $1.05 \mu\Omega\text{cm K}^{-2}$ at 4 T and $0.86 \mu\Omega\text{cm K}^{-2}$ at 8 T. The latter relates to the field dependence of the magneto-resistivity depicted in Fig. 3b which displays a structured, double vaulting field dependence of the magneto-resistivity at temperatures below 2 K.

The initial decrease of the magneto-resistance (compare Fig. 3b) corresponds with a typical behavior of Kondo systems, where magnetic fluctuations of the system become suppressed by increasing magnetic fields; as a consequence, the resistivity decreases. This holds in the entire temperature range studied. For the lowest temperature runs ($T < 2 \text{ K}$), a magnetic field of about 5 T

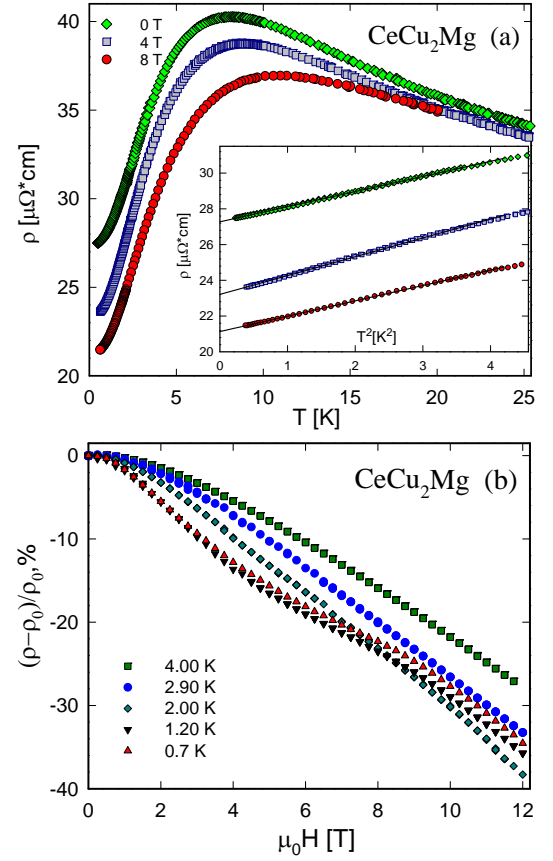


FIG. 3. (Color online) (a) Thermal dependence of the electrical resistivity, $\rho(T)$, measured at various external fields as labeled. Inset: corresponding $\rho(T)$ vs T^2 dependence. (b) Field dependent, relative isothermal magneto-resistivity $[\rho(H) - \rho(H = 0)]/\rho(H = 0)$ measured at various temperatures as labeled.

induces a distinct change of $\Delta\rho/\rho$. This, likely, is associated with changes in the nature of the paramagnetic ground state (see discussion in section IV C).

At higher temperature, $\rho(T)$ exhibits a maximum at $T_{\text{max}}^\rho \approx 8.5 \text{ K}$, see Fig. 3a. In general, such maxima are a characteristics of a Kondo lattice, with $T_K \propto T_{\text{max}}^\rho$; below that temperature the resistivity drops due to onset of coherence among the Kondo scattering centers. Since, however, heat capacity data (see below) refer to a rather small separation of the first excited CEF level from the ground state, T_{max}^ρ is certainly influenced by crystalline electric field effects.

The low value of T_{max}^ρ obtained for CeCu_2Mg , compared with other $\rho(T)$ maxima in Ce compounds, suggests a relatively weak CEF effect with comparable hybridization strength in the lower and GS levels, i.e. $\Delta_1 \approx T_K$. Applied magnetic fields up to $\mu_0 H = 8 \text{ T}$ decrease the maximum moderately and cause an upward shift of $T_{\text{max}}^\rho(H)$, roughly proportional to H^2 (not shown). Above $T_{\text{max}}^\rho(H)$, the typical $\rho(T) \propto -\ln T$ behavior due to Kondo scattering is progressively softened.

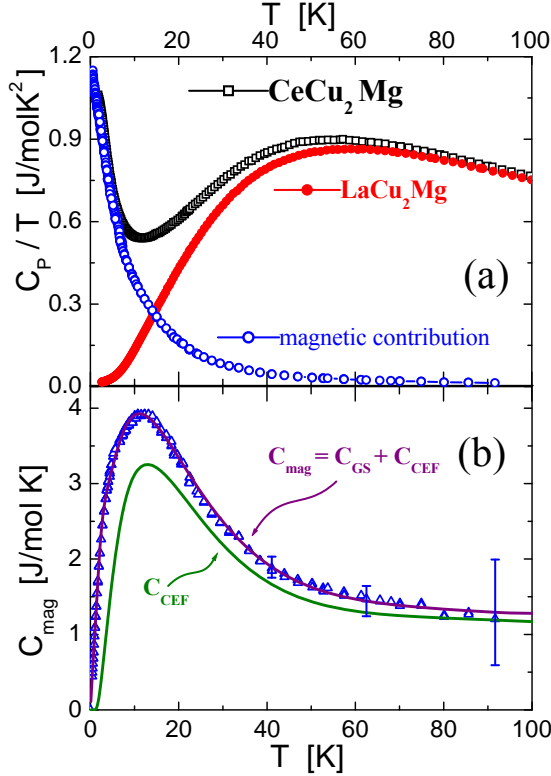


FIG. 4. (Color online) (a) High temperature specific heat up to 130 K, showing the total contribution, C_P/T , compared with the LaCu₂Mg reference for phonon subtraction to obtain the magnetic contribution C_{mag}/T . (b) Analysis of C_{CEF} , the CEF Schottky contribution to the total magnetic contribution C_{mag} , using a set of Schottky anomalies (see text).

D. Specific Heat

Temperature dependent specific heat measurements, performed up to 100 K, are presented in Fig. 4a. The magnetic contribution, C_{mag}/T , is obtained by subtracting phonon and $[6s^25d^1]$ band electron contributions, extracted from the isotopic compound LaCu₂Mg as reported in Ref. [7], from the measured values $C_P(T)/T$ as $C_{\text{mag}} = C_P - C_{\text{LaCu}_2\text{Mg}}$, see Fig. 4a.

In order to discriminate between the GS and the excited CEF level contributions to specific heat, the high temperature $C_{\text{mag}}(T)$ is split as $C_{\text{mag}} = C_{\text{GS}} + C_{\text{CEF}}$. In absence of hybridization (i.e., the Kondo effect), C_{CEF} is properly described by a simple Schottky anomaly [12] because the respective levels are Dirac δ -functions in energy. Taking into account that the CEF splits the six fold Hund's rule state (for the $J = 5/2$ total angular momentum of Ce³⁺) into three Kramer's doublets with respective energies: Δ_1 and Δ_2 , at least two Schottky anomalies are expected to contribute to C_{CEF} . However, due to hybridization effects a standard Schottky anomaly cannot describe the $C_{\text{CEF}}(T)$ dependence properly because of the level broadening due to Kondo interactions.

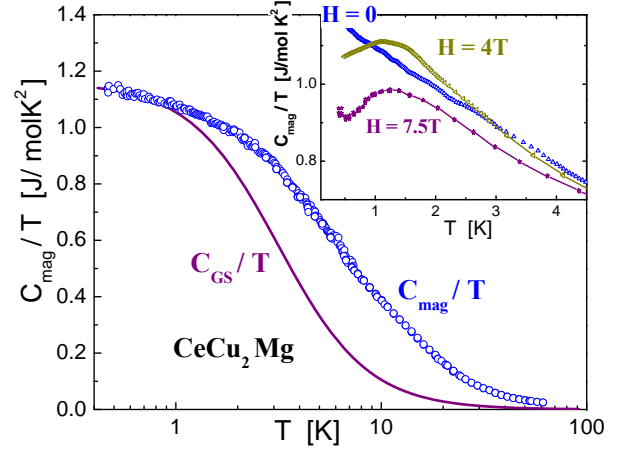


FIG. 5. (Color online) Temperature dependence of C_{mag}/T in a semi-log T representation; solid line: ground state contribution C_{GS}/T computed by subtracting the C_{CEF}/T from C_{mag}/T . Inset: effect of applied magnetic fields upon C_{mag}/T vs T at low temperature.

To take into account that effect, the excited CEF levels are computed as a sum of levels, symmetrically distributed in energy around the nominal values Δ_1 and Δ_2 [13]. This simplified description mimics the broadening ($\delta_i \propto |n(E_F)J_K|^2 T$ [14]) of each doublet centered at Δ_i . The formula applied reads:

$$C_{\text{CEF}}(T) = \sum_i \sum_j A_{i,j} \left[\frac{\left(\frac{\Delta_i + \delta_{i,j}}{2T} \right)}{\cosh \left(\frac{\Delta_i + \delta_{i,j}}{2T} \right)} \right]^2 \quad (2)$$

where $A_{i,j} = R\lambda_i a_{i,j}$ and R is the gas constant. The degeneracy ratio λ_i between the states involved decrease, i.e. $\lambda_1 = 1$ and $\lambda_2 = 1/2$. The coefficients $a_{i,j}$ account for the weight of each level centered at the respective energies Δ_i . For this fit, we used a set of levels composed by a central doublet with $a_{i,j} = 1/2$ and two singlets with $a_{i,j} = 1/4$ which are located at $\Delta_i \pm \delta_{i,j}$.

The result of this fit to the $C_{\text{mag}}(T)$ data is shown in Fig. 4b, with the parameters for the $C_{\text{CEF}}(T)$ contribution, $\Delta_1 \approx 24$ K and $\Delta_2 \sim 200$ K, and the respective effective broadening, $\delta_1 = 15$ K and $\delta_2 \sim 140$ K. The rather low value of Δ_1 is confirmed by the peculiar behavior of this compound discussed in the next section. Since $C_{\text{mag}}(T)$ contains C_{GS} and C_{CEF} , and Eqn. (2) only accounts for the latter, the pure C_{GS} contribution (included in Fig. 4b) is obtained as the difference between the two curves at low temperature, i.e. $C_{\text{GS}} = C_{\text{mag}} - C_{\text{CEF}}$.

Figure 5 displays a semi-logarithmic representation of C_{mag}/T . A monotonous decrease for more than two decades in temperature is observed starting from the heavy fermion value of $C_{\text{mag}}(T \rightarrow 0)/T \approx 1.2$ J/molK². The flattening of $C_{\text{mag}}(T)/T$ vs $\log(T)$ occurs at a similar temperature range as for $M(T)/H$ shown in Fig. 2a. This suggests that both parameters depend on the same

mechanism governing the GS behavior which will be discussed in the next Section.

IV. DISCUSSION

A. Low temperature properties

To gain insight into the magnetic nature of the GS, we have performed specific heat measurements under magnetic fields of $\mu_0 H = 4$ and 7.5 T. An incipient anomaly emerges for $\mu_0 H = 4$ T slightly above 1 K. This anomaly is much better defined for $\mu_0 H = 7.5$ T as it can be observed in the inset of Fig. 5 in comparison to the zero field data. The emergence of this anomaly indicates that Ce^{3+} magnetic moments are progressively polarized by magnetic fields. Notably, magnetic field effects are much weaker than those reported for typical HF whose GS are affected by the Kondo effect. For comparison, one may refer to exemplary HF compounds like $\text{CeCu}_{5.9}\text{Au}_{0.1}$ [15] and $\text{CePd}_{0.15}\text{Rh}_{0.85}$ [16]. These two systems were especially selected because they show similar values of C_{mag}/T at $T \approx 1$ K as CeCu_2Mg , and their behaviors can be compared under a similar magnetic field of $\mu_0 H = 4$ T. In both selected cases C_{mag}/T decreases by more than 50% under a field of 4 T as compared to the zero-field values. On the contrary, in CeCu_2Mg the maximum of the anomaly first exceeds the zero field specific heat and then decreases for 7.5 T. Moreover, no shift occurs in temperature of the anomaly even under $\mu_0 H = 7.5$ T, in clear contrast to both mentioned HF compounds.

Such different behaviors evidence that in the two HF compounds $\text{CeCu}_{5.9}\text{Au}_{0.1}$ and $\text{CePd}_{0.15}\text{Rh}_{0.85}$ magnetic interactions are weakened by the Kondo screening acting on the localized magnetic moments, whereas in CeCu_2Mg the robust (non-screened) magnetic moments simply point on random directions due to the effect of magnetic frustration. Similar behavior occurs in the spin-ice compound $\text{Dy}_2\text{Ti}_2\text{O}_7$ [17]: here an applied magnetic field relieves that frustration by progressively aligning the moments along the field direction.

The symmetry of Ce atomic sites in CeCu_2Mg provides conditions for geometric frustration because the six Ce first magnetic neighbors (at a distance of 4.657 Å) are distributed on the hexagonal lattice [18] of the GdPt_2Sn type structure, whereas the inter-plane distance is 5.094 Å. A characteristic of magnetically frustrated systems is the strong increase of the density of low energy excitations $\propto C_{\text{mag}}/T$ because magnetic correlations try to develop magnetic order as $T \rightarrow 0$, whereas frustration inhibits that possibility impeding magnetic moments alignment.

Based on the magnetic character of these excitations, one may test whether both thermal (C_{mag}/T) and magnetic (χ) parameters are dominated by the same type of excitations of quasi-particles with enhanced m_{eff} which form coherent narrow bands in a periodic Ce-lattice. For such a test, the $\chi(T)/\gamma(T)$ ratio with $\gamma(T) = C_{\text{mag}}(T)/T$

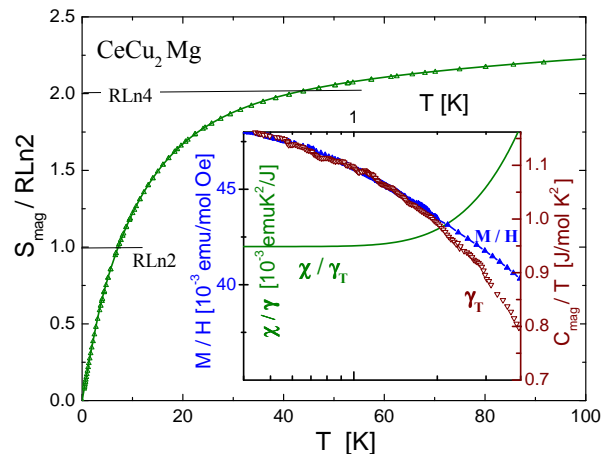


FIG. 6. (Color online) Thermal increase of the entropy normalized to the entropy of a doublet (i.e. $R \ln 2$). The continuous curve is the entropy evaluation from the fit of the specific heat performed in Fig. 5 that extrapolates towards $S = R \ln 6$. Inset: Comparison of low temperature $M/H \equiv \chi$ (outer left axis) and $C_{\text{mag}}(T)/T = \gamma_T$ (right axis). The continuous curve indicates the Wilson-like ratio for the low temperature range (inner left axis).

can be computed and compared with the Wilson-ratio $R_W = 3\mu_B^2/(\pi^2 k_B^2) = 0.014 \text{ emu K}^2/\text{J}$ [19], which strictly applies to FL compounds. Nevertheless, the ratio extracted for this compound: $\chi/\gamma|_{T \rightarrow 0} = 0.042 \text{ emu K}^2/\text{J}$ (see the inset of Fig. 6) is larger than that of other well known HF Ce-compounds like CeCu_6 : $0.020 \text{ emu K}^2/\text{J}$, CeAl_3 : $0.030 \text{ emu K}^2/\text{J}$, and CeCu_2Si_2 : $0.018 \text{ emu K}^2/\text{J}$ [20]. The increase of this ratio at $T \geq 3$ K indicates that the first excited CEF level starts to contribute with a different ratio between its magnetic and thermal components. These features are corroborated by the low temperature $\rho = AT^2$ dependence of the electrical resistivity.

The zero-field value of the Kadowaki-Woods (KW) ratio of CeCu_2Mg , $A/\gamma^2 \simeq 0.64 \times 10^{-6} \mu\Omega\text{cm}(\text{molK}/\text{mJ})^2$, is significantly smaller than that of systems like CeCu_6 with $A/\gamma^2 \sim 10^{-5} \mu\Omega\text{cm}(\text{molK}/\text{mJ})^2$ [21, 22]. Due to the effect of the external magnetic field on C_{mag} , however, the KW ratio of CeCu_2Mg increases almost by a factor of two reaching $A/\gamma^2 \simeq 1.1 \times 10^{-6} \mu\Omega\text{cm}(\text{molK}/\text{mJ})^2$ at 8 T.

B. High temperature properties

The magnetic contribution to the entropy, $S_{\text{mag}}(T)$, follows from $S_{\text{mag}} = \int (C_{\text{mag}}/T) dT$. As shown in Fig. 6 the entropy gain reaches about 87% of the total expected entropy ($R \ln 6$) at 100 K. However, an extrapolation of the entropy, using the fit of the specific heat presented in Fig. 4b, collects more than 95% of the total value (continuous curve in Fig. 6).

The monotonous decrease of $C_{\text{mag}}(T)/T$ with temper-

ature in Fig. 4b indicates that the CEF excited levels are affected by a hybridization broadening comparable to their respective Δ_i splitting. Since these parameters are obtained using a series of Schottky anomalies with a distribution of δ -Dirac type levels, the actual T_{Ki} values are expected to be a little larger because $C_{\text{CEF}}(T \rightarrow 0) \propto \exp(-\Delta/T)$, whereas for a Kondo anomaly one expects to have $C_K(T \rightarrow 0) \propto T$. In any case, the extracted splitting of the first CEF level is notably low compared to other Ce intermetallic systems. To our knowledge, similar low values of Δ_i are only found in CeZn₁₁ [23, 24] and CeCd₁₁ [25], the former showing AF ordering at $T \approx 2$ K and the latter is without magnetic order down to ≈ 1.5 K. The resemblance between their CEF splittings with those of CeCu₂Mg is reflected in a similar $C_{4f}(T)$ dependence at high temperature. However, in the case of CeCu₂Mg a slightly larger scale of T_{Ki} favors the energy overlap between the excited levels. The constant value of $\chi/\gamma T$ up to $T \approx 2$ K allows to estimate a lower limit of the first CEF excited level contribution. In CeZn₁₁ and CeCd₁₁, the low CEF overall splitting is explained by the almost isotropic electronic cage of Ce neighboring atoms [25]: Zn-[4s²] and Cd-[5s²]. This scenario also applies to CeCu₂Mg because of the respective Cu-[4s¹] and Mg-[3s²] electronic character of the ligand atoms. Notice that this compound is a peculiar case among Ce-ternaries because both Ce-ligands have pure *s*-electronic configurations in contrast to the usual *p* or *d* character of some ligands.

C. Frustration and Fermi Liquid coexistence

The low temperature properties of CeCu₂Mg show some peculiar features that can be understood in the frame of the coexistence of two phenomena. Starting with the $\rho(T, H)$ dependence, one can see from Fig. 3a that, while magnetic field induces a decrease of $\rho_0(H)$, the $\rho = AT^2$ dependence is only slightly affected. This behavior indicates that some type of magnetic disorder is progressively reduced, whereas the coherent character remains unchanged.

Coincidentally, $C_{\text{mag}}(T)$ shows a decrease of the intensity of the anomaly centered at $T_{\text{max}} \approx 1.2$ K independently of the applied field (see inset of Fig. 5), whereas a FL signature provided by the Wilson and KW ratios appears at the same range of temperature (see inset of Fig. 6). The decrease of C_{mag}/T at T_{max} suggests a transfer of degrees of freedom from one subsection in the phase space of excitations, i.e. from frustrated spin-liquid-like excitations (see Ref. [26]) essentially contributing to ρ_0 , to another subsection, i.e. Kondo FL-type excitations. The difference in the nature of these excitations does not seem to be that of distinctly different phases separated by a broken symmetry because $\rho(T, H)$ does not behave like in a parallel circuit rather as in a series one. Otherwise, the FL component $\rho_{\text{FL}} = AT^2$ would short-circuit the frustrated one. This suggests that the coexistence of

frustrated RKKY and Kondo interactions is an intrinsic property of the system.

All these features converge in the framework proposed by Coleman and Nevidomskyy [27] where the interplay between frustrated (Q) and Kondo (K) components allows to discuss the physics of HF in a broader perspective. Contrary to the simple picture that these mechanisms exclude each other, the combined 'Q-K' phase diagram shows that a spin liquid, which carries a degree of frustration able to inhibit the formation of magnetic order, may transform into a heavy FL by the increase of the K strength.

Applying these concepts to the present study, one may locate CeCu₂Mg at the region labeled as 'strange metal' in the paramagnetic phase (see Ref. [27]). This possibility is supported by the fact that the magnetic field is able to drive the system in the heavy-FL direction, without changing the Q value significantly as reflected in the $T_{\text{max}} \neq f(H)$ character, but inducing a progressive transfer of degrees of freedom revealed by the reduction of ρ_0 and by a marked increase of the Kadowaki-Woods ratio.

V. CONCLUSIONS

CeCu₂Mg was re-investigated by performing lower temperature transport and thermal measurements complemented with a detailed analysis of the high temperature results. Altogether these data allowed us to shed more light on the peculiar behavior of this compound. The lack of magnetic order is confirmed down to 0.4 K, occurring despite of the robustness of Ce magnetic moments. The relatively low energy scale of Kondo interaction of the ground state is reflected in the enhanced $C_{\text{mag}}/T|_{T \rightarrow 0}$ of this heavy fermion compound that grows up to almost 1.2 J/mol K². The lack of magnetic order is attributed to frustration of magnetic interactions in a hexagonal structure of the magnetic atoms in the plane. This scenario is supported by a specific heat anomaly induced by applied magnetic fields around 1.2 K that decreases in intensity without changing its position in temperature. A small CEF lower level splitting, $\Delta_1 \approx 24$ K, characterizes this compound. Furthermore, it exhibits a comparable Kondo broadening of this level, $\delta_1 \approx 15$ K, that contributes to the physical properties down to quite low temperature.

The temperature dependent electrical resistivity displays a maximum at around 8 K, before entering a coherent state at lower temperature which does not change significantly under magnetic field. While this characteristic for a FL behavior is almost not affected by magnetic field, the residual resistivity decreases by about 30% between 0 and 8 T.

This feature, together with the specific heat behavior under magnetic field, reveal the outstanding characteristic of this compound as a possible experimental example for a system tuned into the 'strange metal' region within

the proposed proposed Q-K (frustration-Kondo) phase diagram for heavy fermion materials.

ACKNOWLEDGMENTS

We acknowledge the support of the HLD-HZDR, member of the European Magnetic Field Laboratory (EMFL). L.S. acknowledges an Ernst Mach stipend from the ÖAD.

† Gerfried Hilscher deceased on May 28th 2016, during finalization of the manuscript.

-
- [1] P. W. Anderson, Phys. Rev. **124**, 41 (1961).
 - [2] G. R. Stewart, Rev. Mod. Phys. **73**, 797 (2001).
 - [3] P. Schlottmann and P. Sacramento, Advances in Physics **42**, 641 (1993).
 - [4] S. Doniach, Physica B+C **91**, 231 (1977).
 - [5] M. Lavagna, C. Lacroix, and M. Cyrot, Physics Letters A **90**, 210 (1982).
 - [6] J. G. Sereni, Journal of Low Temperature Physics **179**, 126 (2015).
 - [7] M. Giovannini, E. Bauer, G. Hilscher, R. Lackner, H. Michor, and A. Saccone, Physica B: Condensed Matter **378–380**, 831 (2006).
 - [8] J. G. Sereni, in *Handbook on the Physics and Chemistry of Rare Earths*, Vol. 15, edited by K. A. Gschneidner Jr. and L. Eyring (Elsevier, 1991) pp. 1–59.
 - [9] Y. Skourski, M. D. Kuz'min, K. P. Skokov, A. V. Andreev, and J. Wosnitza, Phys. Rev. B **83**, 214420 (2011).
 - [10] B. Heying, U. Rodewald, W. Hermes, and R. Pöttgen, Zeitschrift für Naturforschung B **64**, 170 (2014).
 - [11] A. Hewson and J. Rasul, Journal of Physics C: Solid State Physics **16**, 6799 (1983).
 - [12] J. Sereni, in *Reference Module in Materials Science and Materials Engineering* (Elsevier, 2016).
 - [13] J. G. Sereni, P. Pedrazzini, M. Gómez Berisso, A. Chacoma, S. Encina, T. Gruner, N. Caroca-Canales, and C. Geibel, Phys. Rev. B **91**, 174408 (2015).
 - [14] L. C. Lopes and B. Coqblin, Phys. Rev. B **38**, 6807 (1988).
 - [15] H. v. Löhneysen, T. Pietrus, G. Portisch, H. G. Schlager, A. Schröder, M. Sieck, and T. Trappmann, Phys. Rev. Lett. **72**, 3262 (1994).
 - [16] J. Sereni, T. Radu, and A. Pikul, J. Optoelectr. Adv. Mater **10**, 1645 (2008).
 - [17] Z. Hiroi, K. Matsuhira, and M. Ogata, Journal of the Physical Society of Japan **72**, 3045 (2003).
 - [18] A. P. Ramirez, Annual Review of Materials Science **24**, 453 (1994).
 - [19] Z. Fisk, H. R. Ott, T. M. Rice, and J. L. Smith, Nature **320**, 124 (1986).
 - [20] A. Amato, D. Jaccard, J. Flouquet, F. Lapierre, J. L. Tholence, R. A. Fisher, S. E. Lacy, J. A. Olsen, and N. E. Phillips, Journal of Low Temperature Physics **68**, 371 (1987).
 - [21] K. Kadowaki and S. Woods, Solid State Communications **58**, 507 (1986).
 - [22] H. Ott, H. Rudigier, Z. Fisk, J. Willis, and G. Stewart, Solid State Communications **53**, 235 (1985).
 - [23] Y. Nakazawa, M. Ishikawa, S. Noguchi, and K. Okuda, Journal of the Physical Society of Japan **62**, 3003 (1993).
 - [24] H. Hodovanets, S. L. Bud'ko, X. Lin, V. Taufour, M. G. Kim, D. K. Pratt, A. Kreyssig, and P. C. Canfield, Phys. Rev. B **88**, 054410 (2013).
 - [25] J. Tang and K. G. Jr., Journal of Magnetism and Magnetic Materials **75**, 355 (1988).
 - [26] P. W. Anderson, Materials Research Bulletin **8**, 153 (1973).
 - [27] P. Coleman and A. H. Nevidomskyy, Journal of Low Temperature Physics **161**, 182 (2010).